

New Ferroelectric Material for Embedded FRAM LSIs

● Kenji Maruyama ● Masao Kondo ● Sushil K. Singh
● Hiroshi Ishiwara

(Manuscript received April 5, 2007)

The strong growth of information network infrastructures in our society has enabled personal authentication services for electronic money systems and ticketless transportation services to become firmly established. Secure, high-speed, and low power consumption nonvolatile memories will be required for mobile devices used with smart RFID tags and secure IC cards. Ferroelectric random access memory (FRAM) is one of the best choices for these applications. Market needs must be paid attention for these mobile and secure applications. In FRAM research and development, we pursue scalability for increased memory capacity, unlimited read/write cycles, and a wider range of operating voltage, as well as to improve the conventional features of FRAM, we introduce a new ferroelectric material that will enable us to fabricate FRAM in a 90-nm technology node and beyond, by focusing on its superior characteristics. We also describe our plans to commercially produce FRAM devices in the near future.

1. Introduction

The Internet is being rapidly and widely spread on business and off business on our daily activities. The growth of information network infrastructures has enabled the firm establishment of personal authentication services for electronic money systems and ticketless transportation services. Secure and high-speed nonvolatile memories with low power consumption will be required for mobile devices used with smart RFID tags and secure IC cards, which contain IC chips with contactless read and write operations. For such applications, ferroelectric random access memory (FRAM)^{note 1)} represents one of the best choices.

Fujitsu began mass-producing FRAM in

note 1) FRAM (also called FeRAM) devices are nonvolatile memories based on an electrical polarization phenomenon (whereby a charge is retained even without an externally applied voltage). FRAM uses a ferroelectric material to hold data.

1999 and has shipped more than 500 million chips up to May, 2007. FRAM is completely new devices on principles of operation, compared with the conventional nonvolatile memories such as EEPROM and flash memory. Therefore, FRAM has a capability to create a new market, in addition to expanding the market for replacing existing products.

We have to pay attention to the market needs for the mobile and secure application. In FRAM development, we pursue scalability for increased memory capacity, unlimited read/write cycles, and a wider range of operating voltage, as well as to improve the existing features of FRAM.

We introduce a new ferroelectric material that will enable us to fabricate FRAM in a 90-nm technology node and beyond, by focusing on its superior characteristics. We also describe our plans to commercially produce FRAM devices in the near future.

The Ministry of Education, Culture, Sports,

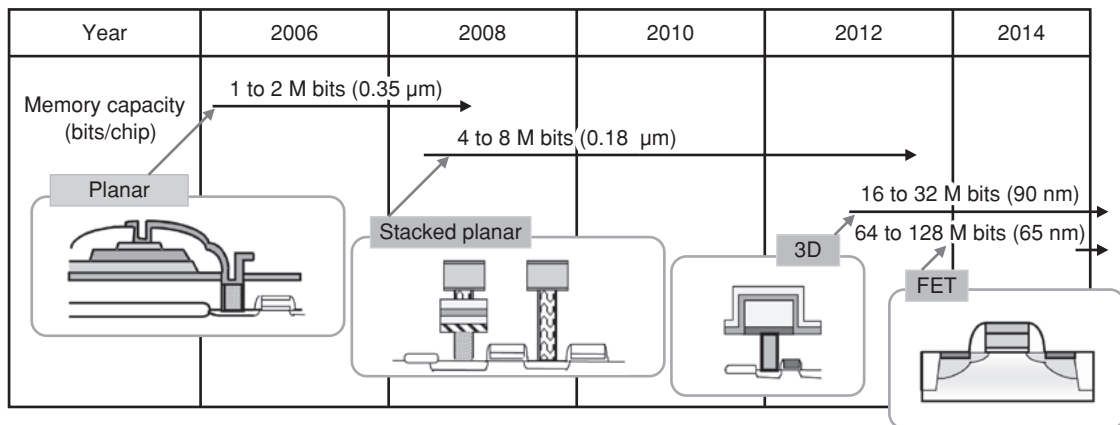


Figure 1
FRAM technology roadmap.

Science and Technology commissioned the Tokyo Institute of Technology (Tokyo-Tech) to conduct part of this technological research based on funding to promote science and technology. This paper looks at the achievements of joint research conducted between the Tokyo Institute of Technology and Fujitsu Laboratories Ltd. based on industry-university research collaborative partnership.¹⁾

2. FRAM technology

2.1 Policy of FRAM technology development

Fujitsu began mass-production of FRAM in 1999 using a 0.5-μm technology node and currently manufactures 2 Mbit FRAM using a 0.35-μm technology node.²⁾ Given its ideal memory properties, such as very low power consumption and high-speed read/write performance, FRAM has been applied to LSIs for IC cards, RFID tags, smart cards, and for alternate memory addressing with battery backup.

To further expand FRAM applications, it is essential to develop technology for increasing memory capacity, reducing operating voltage, and increasing the read/write cycles. It is also necessary to develop services and applications made

possible only by using FRAM and the related underlying systems. The actualization of 90-nm FRAM technology through integration technology will enable increased memory capacity and significantly reduced operating voltage, and allow the reuse of an abundant design library already developed for logic LSIs. This will lead to shorter development periods and deadlines for FRAM-embedded devices, and allow us to promptly release products.

2.2 Progress of FRAM technology in material and structure

When we began mass-production of FRAM, the process was based on the 0.5-μm technology node. The technology was then scaled down to 0.35-μm and is currently at 0.18-μm generation.^{3),4)}

Figure 1 shows the FRAM technology roadmap. It is assumed that the full extent of integration will be reached using the existing material and structure by 2009 or shortly thereafter. The existing ferroelectric capacitor — $\text{Pb}(\text{Zr,Ti})\text{O}_3$ (PZT) — is limited regarding its remanent polarization (Q_{sw}).^{note 2)} A planar stack struc-

note 2) Q_{sw} is the charge equivalent to twice the remanent polarization P_r (the electric charge when applied voltage is removed).

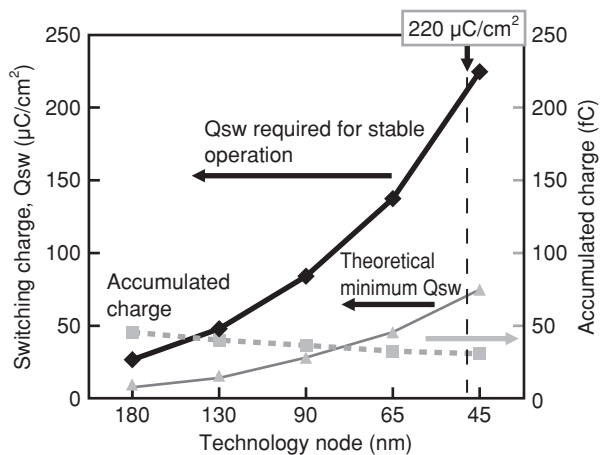


Figure 2
Q_{sw} required for stable operation of 1T1C FRAM in stacked planar capacitor.

ured 1T1C (1 Transistor/1 Capacitor) FRAM is considered to have a lower limit at 0.13 μm with regard to scalability. **Figure 2** shows the Q_{sw} required for stable operation of five generations of 1T1C FRAM with a planar stack capacitor. For instance, the Q_{sw} required for stable operation using a 90-nm technology node is estimated to be 84 μC/cm². Although the PZT material has a larger Q_{sw} value, fabrication through the semiconductor process restricts FRAM to a maximum of 40 μC/cm². Therefore, a breakthrough is necessary to fabricate FRAM based on the 90-nm technology node using PZT.

One method of overcoming the Q_{sw} limit regarding PZT is to expand the surface area by assembling a capacitor into a 3D structure. However, unlike dynamic random access memory (DRAM) having a similar structure, in FRAM, a ferroelectric layer forming a capacitor must be crystals oriented in the same direction and not amorphous. The 3D pattern requires a ferroelectric crystal layer on the side walls as well as on the bottom surface. While it is possible to expand the surface area, obtaining the required Q_{sw} may prove extremely challenging because it is difficult to arrange the crystal orientation completely.

While FRAM with an FET-type capacitor

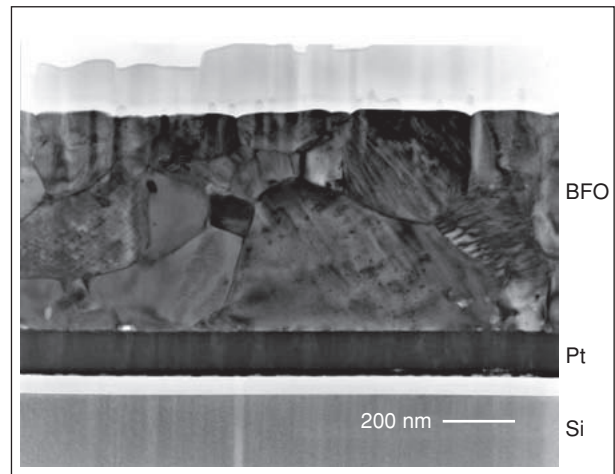


Figure 3
Cross-sectional TEM image of Mn-doped BFO layer on Pt layer.

enables a further reduction in cell dimensions and offers the advantage of low-voltage operation, there are currently many problems regarding the development of the required material and process technology. Since such development is predicted in a long range, practical use of such FRAM using a 65-nm technology node and beyond is expected.

3. Characteristics of Mn-doped BFO

We have successfully developed a new ferroelectric material for a 90-nm technology node and beyond that consists of 5% Mn-doped BFO (BiFeO₃, bismuth ferrite).⁵⁾ We substituted some of the Fe ions with Mn ions to decrease the leakage current in the BFO film at room temperature and increase the withstand voltage. Our experimental results revealed that 5% Mn-doping to BFO achieves a Q_{sw} value of 180 to 220 μC/cm², which is five times larger than that of PZT. The leakage current due to reduced hopping conduction by the electron of Fe ions was suppressed by adding Mn ions having a larger number of valence than Fe ions and substituting part of the Fe ions. As a result, we obtained the large Q_{sw} in the original nature of BFO.^{6,7)} **Figure 3** shows a cross-sectional TEM image

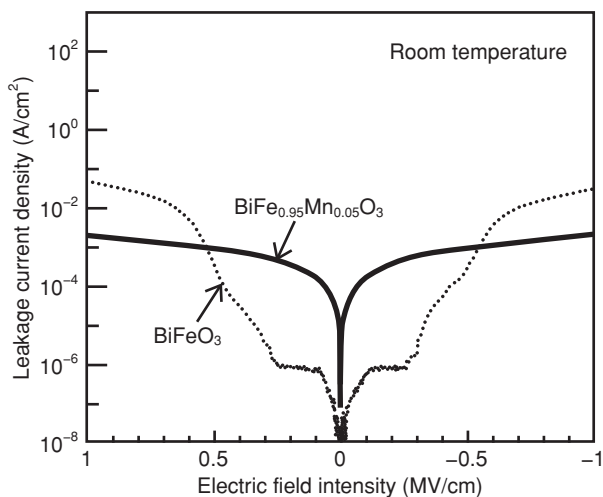


Figure 4
Dependence of leakage current density on applied electric field in Mn-doped BFO.

of the Mn-doped BFO layer prepared by the sol-gel/spin-coating method that is used to form a BFO thin film with thickness of 400 nm.

Figure 4 shows the dependence of the leakage current density on the applied electric field in a Mn-doped BFO at room temperature. The leakage current in Mn-undoped BFO film at electric field up to about 0.25 MV/cm is low, but increases abruptly above 0.25 MV/cm. The effect of Mn addition results in a moderate increase in current in the low electric field region of less than 0.5 MV/cm. The withstand voltage in the film is also improved, and the current at electric field up to about 1 MV/cm exhibits a gradual increase.

Figure 5 shows the remanent polarization ($Pr = Q_{sw}/2$) versus electric field in a 5% Mn-doped BFO at room temperature. Due to its high leakage current, the hysteresis characteristics of undoped BFO could not be obtained at room temperature. Mn-doped BFO shows a square-shaped hysteresis at room temperature, however, as well as a high Q_{sw} of $220 \mu\text{C}/\text{cm}^2$. Mn-doped BFO has a sufficient Q_{sw} for stable operation in consideration of 65-nm FRAM technology node, except difficulty to achieve polarization reversal (coercive electric field,

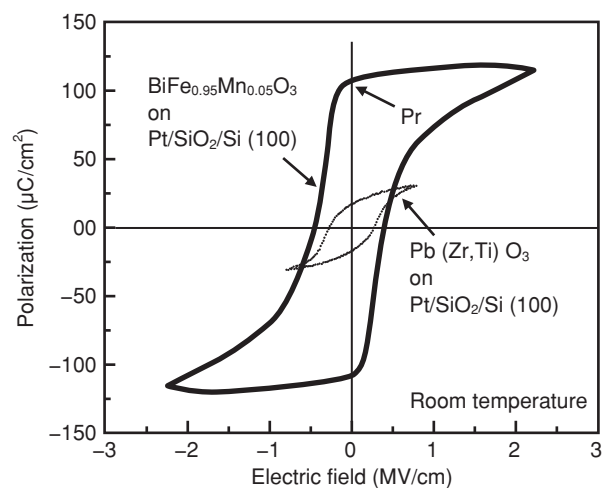


Figure 5
Hysteresis characteristics in Mn-doped BFO.

$V_c^{\text{note 3}}$) with the comparatively low voltage applied in 65-nm generation circuits due to the high V_c of current BFO films.

In addition, the relative dielectric constant of BFO is one-fourth that of the conventional ferroelectric material like PZT, and its Curie temperature^{note 4)} is 800°C , which is more than double that of the conventional material. These properties advance high-speed read/write and high-temperature operation, and indicate the potential for developing FRAM applications on a much wider scale.

4. Future issues

Mn-doped BFO shows a large Q_{sw} of 180 to $220 \mu\text{C}/\text{cm}^2$ and exhibits a low leakage current level of $1 \times 10^{-4} \text{ A}/\text{cm}^2$ at room temperature. These characteristics make its application to 1T1C planar capacitor structured FRAM up to the 65-nm generation possible. Characteristics

note 3) Voltage applied to remove the residual surface charge of a ferroelectric material.

note 4) The Curie temperature is the temperature at which polarization is not caused by changes in the atomic configuration of a ferroelectric material. FRAM loses its nonvolatility at and above the Curie temperature.

such as the Q_{sw} and leakage current, however, have only reached an acceptable level and simply represent the baseline characteristics at the material and property levels. To commercialize FRAM using BFO, the following problems should be solved:

1) Reduction of V_c

FRAM using a 90-nm technology node and beyond requires an operating voltage of less than 1.2 V. To reverse polarization with this voltage, we must enhance the electric field intensity by reducing the thickness of the ferroelectric layer, improve the characteristics of coercive electric field, and reduce the V_c of the BFO.

2) Low temperature deposition

The lower-limit of BFO film deposition temperature is determined by the crystallization temperature of the BFO film, and is about 600 °C. To fabricate FRAM using a 90-nm technology node and beyond, we need to lower the temperature of film deposition by, for example, improving the sol-gel solution or adding a dopant other than Mn.

3) Selection of passivation film to prevent Fe diffusion

Fe is considered an undesirable element in the silicon process because it rapidly diffuses into silicon substrates. Therefore, the ferroelectric oxide layers are covered with passivation films for protection to avoid the deoxidation by hydrogen from invading during the fabrication process. This passivation film also has to prevent the diffusion of Fe.

We have been developing technologies to find solutions to these problems. Moreover, we have been promoting research and development for fabricating FRAM using BFO materials. It is additionally important to find a deposition method for mass production, other than the sol-gel method, as well as to develop an oxide electrode material that prevents the degradation of properties.

5. Conclusion

This paper described our newly developed

Mn-doped BFO that enables us to fabricate FRAM in a 65-nm technology node with a device structure similar to that of FRAM being produced using 0.18- μm technology. This new material is expected to enable fabrication using a 90-nm technology node and beyond and a large memory capacity up to 2014. With further development of BFO, FRAM having capacities exceeding 256 M bits and a memory cell capacity that is two orders of magnitude higher than the current capacity of 1 M bits can be realized in the future. These higher capacities will allow FRAM to be used in hybrid HDDs for computers, storage caches, electronic paper devices, and document viewers that let users store and browse information that is traditionally written on plain paper, as well as in IC cards. Moreover, we expect to significantly help reduce the power consumption of electronic devices. In the future, we will establish a BFO material and process technology for embedded FRAM LSIs and work toward achieving the practical use of FRAM in a 90-nm technology node by 2011.

References

- 1) S. Yoshikawa: Proposal for new industry-university research collaborative partnership for enhancing industrial competitiveness. (in Japanese), *OYO BUTURI*, **75**, 1, p.69-71 (2006).
- 2) T. Yamazaki et al.: Advanced 0.5 μm FRAM device technology with full compatibility of halfmicron CMOS logic device. IEDM Tech. Dig., December 1997, p.613-616.
- 3) Y. Horii et al.: 4 M bit embedded FRAM for high performance system on chip (SoC) with large switching charge, reliable retention and high imprint resistance. IEDM Tech. Dig., December 2002, p.539-542.
- 4) Y. Nagano et al.: 0.18 μm SBT-Based Embedded FeRAM Operating at a Low Voltage of 1.1 V. Symp. VLSI Technol. 2003, p.171-172.
- 5) S. K. Singh et al.: Room temperature ferroelectric properties of Mn-substituted BiFeO₃ thin films deposited on Pt electrodes using chemical solution deposition. *Appl. Phys. Lett.*, **88**, 262908 (2006).
- 6) J. Wang et al.: Epitaxial BiFeO₃ Multiferroic Thin Film Heterostructures. *Science*, **299**, No.5613, p.1719-1722 (2003).
- 7) K. Y. Yun et al.: Structural and multiferroic properties of BiFeO₃ thin films at room temperature. *J. Appl. Phys.*, **96**, p.3399-3403 (2004).



Kenji Maruyama, *Fujitsu Laboratories Ltd.*

Dr. Maruyama received the B.E. degree in Applied Physics from the University of Tokyo, Japan in 1981 and the Ph.D. degree in Material Science from Tohoku University, Sendai, Japan in 2000. He joined Fujitsu Laboratories Ltd., Atsugi, Japan in 1981 and has been engaged in research and development of thin film ferroelectric materials for non-volatile memory applications. He is a member of the Institute of Electrical and Electronics Engineers (IEEE) and a member of the Japan Society of Applied Physics.

als for non-volatile memory applications. He is a member of the Institute of Electrical and Electronics Engineers (IEEE) and a member of the Japan Society of Applied Physics.

E-mail: maruyama@labs.fujitsu.com



Sushil K. Singh, *Tokyo Institute of Technology.*

Dr. Singh is a senior researcher at Tokyo Tech. and working in Next Generation FeRAM project jointly run by Tokyo Tech. and Fujitsu. He received his PhD degree in Physics at Barkatullah University, Bhopal in 1993. In 1994, he received a Leverhulme postdoctoral fellowship to work at Warwick University on oxide thin films (CMR materials). He joined as a faculty at G. G. D. University, Bilaspur in 1997. He has been awarded Commonwealth teacher fellowship in 2001. Tokyo Tech. invited him as a JSPS invited fellow in 2004 and is being engaged in research of ferroelectric thin films for non-volatile memory applications. His current research interests include multiferroic thin films for electronic device fabrication such as memory and spintronic devices.

He joined as a faculty at G. G. D. University, Bilaspur in 1997. He has been awarded Commonwealth teacher fellowship in 2001. Tokyo Tech. invited him as a JSPS invited fellow in 2004 and is being engaged in research of ferroelectric thin films for non-volatile memory applications. His current research interests include multiferroic thin films for electronic device fabrication such as memory and spintronic devices.

E-mail: singhsushil.k.aa@m.titech.ac.jp



Masao Kondo, *Fujitsu Laboratories Ltd.*

Dr. Kondo received the B.E., M.E., and Dr. degrees in Engineering of Inorganic Materials from Tokyo Institute of Technology, Tokyo, Japan in 1990, 1992, and 1995, respectively. He joined Fujitsu Laboratories Ltd., Atsugi, Japan in 1995, where he had been engaged in research and development of piezoelectric ceramics, piezoelectric actuators, and ferroelectric thin films until 2006. Since 2007, he has been engaged in R&D strategy and planning at the headquarters in Kawasaki. He is a member of the Japan Society of Applied Physics (JSAP), and the Ceramic Society of Japan (CSJ).

He has been engaged in R&D strategy and planning at the headquarters in Kawasaki. He is a member of the Japan Society of Applied Physics (JSAP), and the Ceramic Society of Japan (CSJ).

E-mail: condor@labs.fujitsu.com



Hiroshi Ishiwara, *Tokyo Institute of Technology.*

Dr. Ishiwara received the B.S., M.S., and Ph.D. degrees in electronic engineering from Tokyo Institute of Technology, Tokyo, Japan, in 1968, 1970, and 1973, respectively. He was with the Tokyo Institute of Technology, as Research Associate (1973-1976), Associate Professor (1976-1989), and Professor (1989-present). From April 2004 to March 2006, he was the Dean of professor at Interdisciplinary Graduate School of Science and Engineering. His research interests are in the areas of device and process technologies in integrated circuits, and at present he is particularly concerned with ferroelectric memories. He is a fellow of the Institute of Electrical and Electronics Engineers and the Institute of Electronics, Information and Communication Engineers, as well as a member of the Materials Research Society, the Electrochemical Society, the Japan Society of Applied Physics, and the Institute of Electrical Engineers of Japan.

From April 2004 to March 2006, he was the Dean of professor at Interdisciplinary Graduate School of Science and Engineering. His research interests are in the areas of device and process technologies in integrated circuits, and at present he is particularly concerned with ferroelectric memories. He is a fellow of the Institute of Electrical and Electronics Engineers and the Institute of Electronics, Information and Communication Engineers, as well as a member of the Materials Research Society, the Electrochemical Society, the Japan Society of Applied Physics, and the Institute of Electrical Engineers of Japan.

E-mail: ishiwara.h.aa@m.titech.ac.jp